

PAPER

View Article Online
View Journal



Cite this: DOI: 10.1039/d0ee01279c

Selective CO production from aqueous CO₂ using a Cu₉₆In₄ catalyst and its integration into a bias-free solar perovskite–BiVO₄ tandem device†

Motiar Rahaman,^a Virgil Andrei,^a Chanon Pornrungroj,^a Demelza Wright,^{ab} Jeremy J. Baumberg^b and Erwin Reisner^{*,a}

Sunlight-driven production of fuels is attracting attention for the generation of storable renewable energy, but the design of selective catalysts for CO₂ utilization and the assembly of unassisted devices for selective and efficient CO₂-to-fuel conversion remains challenging. In this study, we report a bimetallic Cu₉₆In₄ alloy with a dendritic foam morphology for the reduction of aqueous CO₂ to CO at an onset potential of −0.3 V vs. the reversible hydrogen electrode (RHE) and with >70% selectivity. Operando Raman spectroscopy reveals weaker *CO adsorption on the Cu₉₆In₄ alloy surface compared to bare Cu and supports the immediate release of CO(g) as the product from the electrocatalyst surface. The Cu₉₆In₄ catalyst is subsequently employed in an overall bias-free tandem device for CO₂ conversion using water as an electron donor. The buried photovoltaic-biased photoelectrochemical cell relies on state-of-the-art triple-cation mixed halide perovskite and BiVO₄ photoabsorbers that can also be assembled in an artificial leaf configuration. The device reaches a solar-to-CO energy conversion efficiency of 0.19% with a selectivity of 75% for CO after 10 h simulated sunlight irradiation using bias-free conditions. The buried perovskite|Cu₉₆In₄ cathode shows robust, unaltered PEC activity at different solar intensities, which also allows it to function under low and diffuse sunlight. This study highlights the potential of alloying to improve catalytic performance and strategies to integrate such catalysts into solar-driven PEC devices.

Received 23rd April 2020,
Accepted 17th August 2020

DOI: 10.1039/d0ee01279c

rsc.li/ees

Broader context

Storage of solar energy into chemical energy vectors provides a pathway to a sustainable, circular economy by diminishing the global energy reliance on fossil fuels. Sunlight is the most abundant and exploitable energy source and can power the direct conversion of the greenhouse gas CO₂ and H₂O into renewable fuels. However, the practical usage of this technology still faces several challenges such as developing efficient catalysts and light harvesters and their combination to produce solar fuels in a selective, scalable, and cost-effective manner. Here, we present a novel approach of interfacing an inexpensive and selective Cu alloy catalyst into a state-of-the-art lead halide perovskite|BiVO₄ tandem device for sunlight-driven CO₂-to-CO conversion without the need of any other energy input. Solar fuel generators that synthesize CO are of interest as this product can be converted into liquid hydrocarbon fuels by the Fischer–Tropsch process. The light-driven device shows robust performance towards CO production over a wide range of light intensities, which indicates its compatibility for operation under varying daylight conditions. This prototype presents a proof-of-concept for the integration of selective transition metal catalysts into solar fuel devices and motivates the development of solar reactors for multicarbon products from CO₂ in the future.

Introduction

The conversion of CO₂ into value-added products is of contemporary interest for the development of a carbon-neutral

energy cycle, but the underlying catalytic reaction is thermodynamically challenging and kinetically complex. Sunlight is an abundant and readily available energy source that can be directly used for the generation of useful molecules from CO₂, thereby storing energy in the chemical bonds of the product.^{1,2} The bio-inspired process of converting CO₂ and H₂O into energy carriers with sunlight is known as artificial photosynthesis.^{3–5} Among all the possible CO₂ reduction products, CO has particular importance since it can be combined with H₂ to form alcohols and long chain hydrocarbons by established industrial processes.^{6,7} A substantial energy input is required to obtain CO electrochemically, but light-driven CO formation

^a Department of Chemistry, University of Cambridge, Lensfield Road, Cambridge CB2 1EW, UK. E-mail: reisner@ch.cam.ac.uk; Web: <http://www-reisner.ch.cam.ac.uk>; Tel: +44-1223336323

^b NanoPhotonics Centre, Cavendish Laboratory, Department of Physics, University of Cambridge, JJ Thomson Avenue, Cambridge CB3 0HE, UK

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ee01279c. Raw data related to this publication are available at the University of Cambridge data repository: <https://doi.org/10.17863/CAM.56420>.



presents an alternative and sustainable way for its production from sunlight.

Lead halide perovskites are emerging light absorbers for solar fuel production and can either be indirectly coupled as external photovoltaic cells to an electrolyzer or integrated as encapsulated component in a photoelectrochemical (PEC) device.^{8–17} The combination of a buried perovskite-biased cathode with a water oxidizing BiVO₄ photoanode in a tandem configuration (perovskite||BiVO₄) can perform water splitting under bias-free conditions.^{18–20} Recently, we have reported a molecular catalyst-based perovskite||BiVO₄ tandem system for unassisted CO₂ reduction to syngas using water as an electron donor.²¹ However, the PEC tandem device showed a limited bias-free solar-to-CO conversion efficiency of 0.02%, with a relatively low CO selectivity (CO:H₂ ratio of ~3:10). Therefore, an improved catalyst and a redesign of the device architecture are required to increase the CO₂ reduction activity and selectivity of the PEC tandems.

In this study, a bimetallic alloy is employed as an efficient catalyst on an improved perovskite||BiVO₄ tandem to achieve an increased efficiency and selectivity for solar CO₂ conversion under bias-free conditions. We report the design of a Cu₉₆In₄ alloy with a unique dendritic foam morphology, which confers high selectivity toward CO production at low overpotentials. To improve the onset bias of the PEC tandem device, we also incorporate an additional hole-transporting layer into the perovskite architecture. The newly designed Cu–In alloy catalyst was employed on electrodes, perovskite-biased cathodes, and perovskite||BiVO₄ PEC tandems for bias-free selective CO formation coupled to O₂ evolution. Fig. 1a shows the schematic diagram of a standalone tandem device, revealing the perovskite device architecture, metal alloy catalyst morphology, BiVO₄ photoanode and their assembly.

Results and discussion

Preparation and characterization of the catalyst

Transition metal alloys, especially Cu-based bimetallic systems are well-known as potentially active and inexpensive catalysts

for selective electrochemical CO₂ conversion.^{22–25} Here, we have used a template assisted electrodeposition method to prepare a bimetallic copper–indium foam catalyst. Galvanostatic electrodeposition was carried out by applying -3 A cm^{-2} using a deposition bath containing Cu²⁺ and In³⁺ precursors in aqueous H₂SO₄ (1.5 M), where the co-produced H₂ bubbles acted as template for the porous architecture (see Fig. S1 and Methods for details, ESI†).^{26,27}

Scanning electron microscopy (SEM) shows a porous structure of the catalyst with an average surface pore size of $35 \pm 4.5 \mu\text{m}$ (Fig. 1b), whereas high resolution transmission electron microscopy (HR-TEM) reveals that the pore side walls consist of dendritic fern-like structures (Fig. 1c). The Cu:In metallic ratio of the alloy was found to be ~96:4 by inductively coupled plasma optical emission spectrometry (ICP-OES) analysis and energy-dispersive X-ray spectroscopy (EDX) mapping (in both TEM and SEM mode; Fig. S2, ESI†). As In is a scarce element that is commonly used by the electronics industry, we calculated the amount of In present in our catalyst. Gravimetric analyses show that 1 cm² active area contains around 1.7 mg of catalyst which corresponds to only ~70 μg of metallic In, considering the bulk composition of Cu and In as 96:4 according to the ICP-OES and EDX analyses. Scanning transmission electron microscopy (STEM) mapping shows a uniform distribution of Cu and In on the branches of the dendrite nanostructures (Fig. 1d). The selected area electron diffraction (SAED) pattern in Fig. 1e indicates a face centered cubic (fcc) lattice system, where a particular preferential crystal plane orientation in the bimetallic polycrystalline material is shown. Powder X-ray diffraction (XRD) analysis of the as-prepared material indicates the presence of a major CuIn alloy phase, as well as some residual Cu and Cu₂O (from aerial oxidation) phases in the catalyst (Fig. 1f; JCPDS: 42-1476 and 35-1150 for CuIn alloy, 85-1326 for Cu, and 75-1531 for Cu₂O). No surface contamination (traces of other metals) was identified by X-ray photoelectron spectroscopy (XPS) survey analysis (Fig. S3, ESI†). The Cu 2p_{1/2}, Cu 2p_{3/2} peaks from the Cu region and In 3d_{3/2}, In 3d_{5/2} peaks from In region are shown in Fig. 1g and h, respectively, which indicates the presence of both metals on the surface of the material. The XPS study also

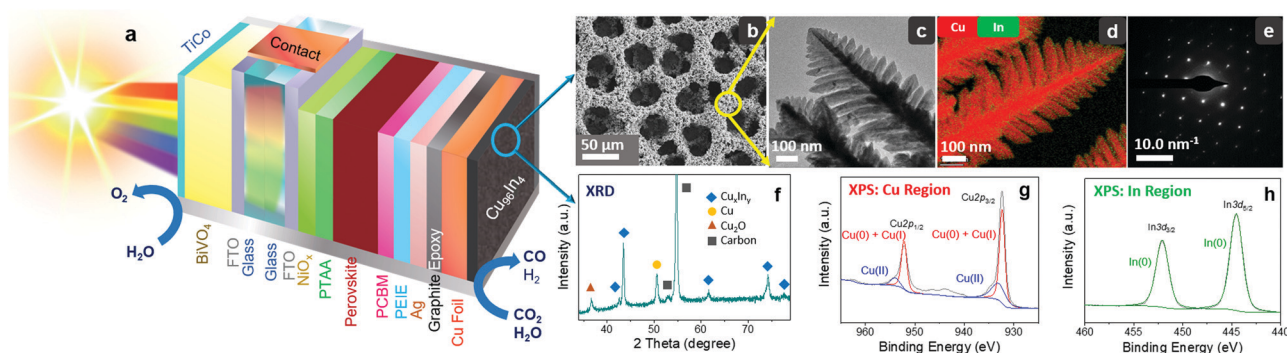


Fig. 1 Schematic model illustrating a BiVO₄||perovskite|Cu₉₆In₄ tandem device assembled in a leaf configuration (a). The CuIn catalyst is characterized by low-resolution SEM (b), high-resolution TEM (c), STEM mapping (d), SAED pattern analysis (e), powder XRD analysis (f), and XPS analysis in the Cu (g) and In (h) regions. The Cu 2p peaks (g) are deconvoluted into Cu(0) + Cu(I) peaks (red) and a Cu(II) peak (blue) as indicated in the figure. Cu(I) and Cu(II) components are assigned to surface oxide formation due to aerial oxidation.



indicates the presence of Cu_xO components on the surface due to aerial oxidation. However, these residual oxide phases are unstable under cathodic conditions as they are being reduced back to the metallic state when applying a negative potential (see below). We termed the material as a $\text{Cu}_{96}\text{In}_4$ alloy to indicate the actual bulk composition of Cu and In and also to denote the major active catalytic phase, which is a mixed alloy.



Electrochemical analysis of the catalyst

The $\text{Cu}_{96}\text{In}_4$ alloy was electrochemically characterized by linear sweep voltammetry (LSV) and controlled potential electrolysis (CPE), using a three electrode configuration with a Pt mesh counter and $\text{Ag}/\text{AgCl}(\text{Satd. NaCl})$ reference electrode. Fig. 2a shows LSV curves in N_2 saturated (green, pH 8.3) and CO_2 saturated (red, pH 7.2) 0.5 M aqueous KHCO_3 electrolyte solution. The onset potential (at approximately -0.3 V vs. RHE) in CO_2 saturated electrolyte solution shows a positive shift compared to that in N_2 saturated solution, which indicates that the catalytic activity of the material starts at a low overpotential.

CPE under CO_2 at applied potentials ranging from -0.3 V to -0.6 V vs. RHE shows CO as the dominant product (Fig. 2b). The faradaic efficiency for CO (FE_{CO}) was roughly constant over the applied potential window with a maximum of $(78.1 \pm 2.1)\%$ at -0.4 V vs. RHE. The remaining charge was consumed for the generation of H_2 as a secondary product from proton reduction with an overall combined FE for CO and H_2 ($\text{FE}_{\text{CO}+\text{H}_2}$) of close to 100% (Table S1, ESI†). Cu is the only metal that can form multicarbon products from CO_2 , whereas In is known as formate producing metal.²⁸ Selective CO formation from CO_2 without any multicarbon products at more negative potentials (-0.6 V vs. RHE) supports the assignment of the active catalyst as a mixed alloy phase. The total amount of gaseous products gradually increased with more negative applied potentials (Fig. S4 and Table S2, ESI†). To study the effect of catalyst composition on the selectivity, CPE was carried out at -0.4 V vs. RHE with pristine Cu, $\text{Cu}_{96}\text{In}_4$, and $\text{Cu}_{90}\text{In}_{10}$ foam (Fig. 2c). Pristine Cu produced H_2 with a FE (FE_{H_2}) of $(77.0 \pm 4.2)\%$, whereas $\text{Cu}_{90}\text{In}_{10}$ shows a FE_{CO} of $(63.8 \pm 4.6)\%$ (see Tables S3 and S4 for FEs and amounts of products, Fig. S5 for SEM and EDX analysis of $\text{Cu}_{90}\text{In}_{10}$, ESI†). Hence, an optimal catalytic behavior

for selective CO production can be achieved by incorporating 4% In into Cu.

The conversion of CO_2 to CO in aqueous medium depends on the interaction of the reaction intermediates with the active sites of the catalyst material. It is typically considered to consist of the following elementary steps:^{29–31}



where $*$ denotes a vacant active site on the catalyst surface. The formation of CO depends on the stabilization and reduction of the $*\text{COOH}$ intermediate as well as the ability of the catalyst to release $*\text{CO}$ as a gaseous product. Recent DFT studies show that inclusion of In to Cu improves the stability of the intermediate and thus facilitates the CO production.^{25,32} On the other hand, much higher energy is required for $*\text{H}$ adsorption on a CuIn surface compared to Cu, making it less active for H_2 evolution (Fig. 2c). Fig. 3a shows a schematic diagram of a possible CO forming mechanism on the CuIn surface, where different adsorbed species are shown systematically.

Operando Raman spectroscopy

To identify intermediate species and characterize the exposed alloy phase on the catalyst surface, we performed operando Raman spectroscopy during stepped-potential chronoamperometry. Fig. 3b and c show operando Raman spectra of Cu and $\text{Cu}_{96}\text{In}_4$, respectively, in CO_2 saturated 0.5 M aqueous KHCO_3 showing the $\text{C}\equiv\text{O}$ stretching mode, $\nu(\text{CO})$. The full range spectra are presented in Fig. S6 (ESI†), where reduction of the Cu_xO layer under cathodic potentials as well as $\text{CO}_3^{2-}/\text{HCO}_3^-$ adsorption peaks are shown. For the pure Cu sample, a broad band appeared when the potential was stepped to -0.2 V vs. RHE at around 2050 cm^{-1} , which can be deconvoluted into two overlapping bands at 2005 and 2052 cm^{-1} (Fig. 3b and d). The lower frequency band (LFB, 2005 cm^{-1}) has been previously assigned as atop bound CO on terraces, based on Cu(100) surface studies.^{33,34} The higher frequency band (HFB, 2052 cm^{-1}) has been more confidently assigned as undercoordinated defect

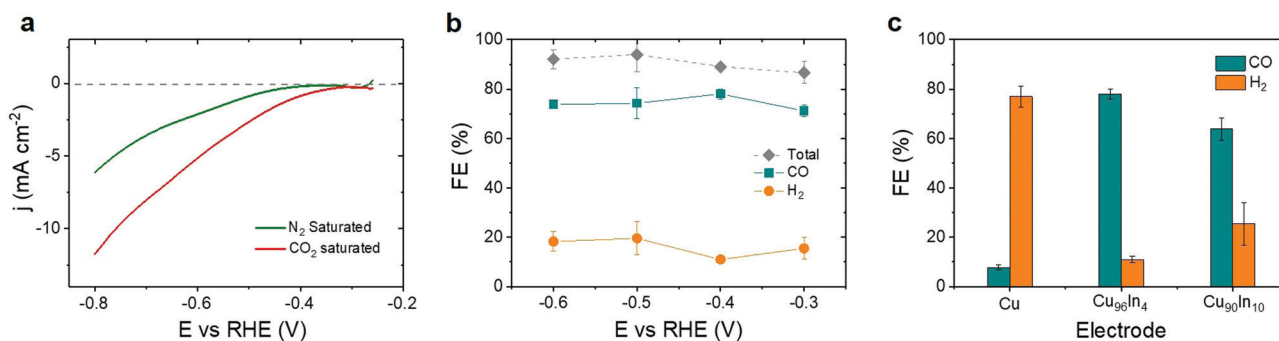


Fig. 2 Electrochemistry of the $\text{Cu}_{96}\text{In}_4$ alloy catalyst: (a) LSV in N_2 and CO_2 saturated 0.5 M KHCO_3 electrolyte at a scan rate of 10 mV s^{-1} , (b) CPE showing the potential dependent faradaic efficiency of CO and H_2 on the $\text{Cu}_{96}\text{In}_4$ catalyst, (c) composition dependent electrochemical performance of pure Cu and different Cu_xIn_y alloys at -0.4 V vs. RHE. CPE in (b) and (c) was carried out in CO_2 saturated aqueous 0.5 M KHCO_3 medium (pH 7.2) for 4 h at room temperature.



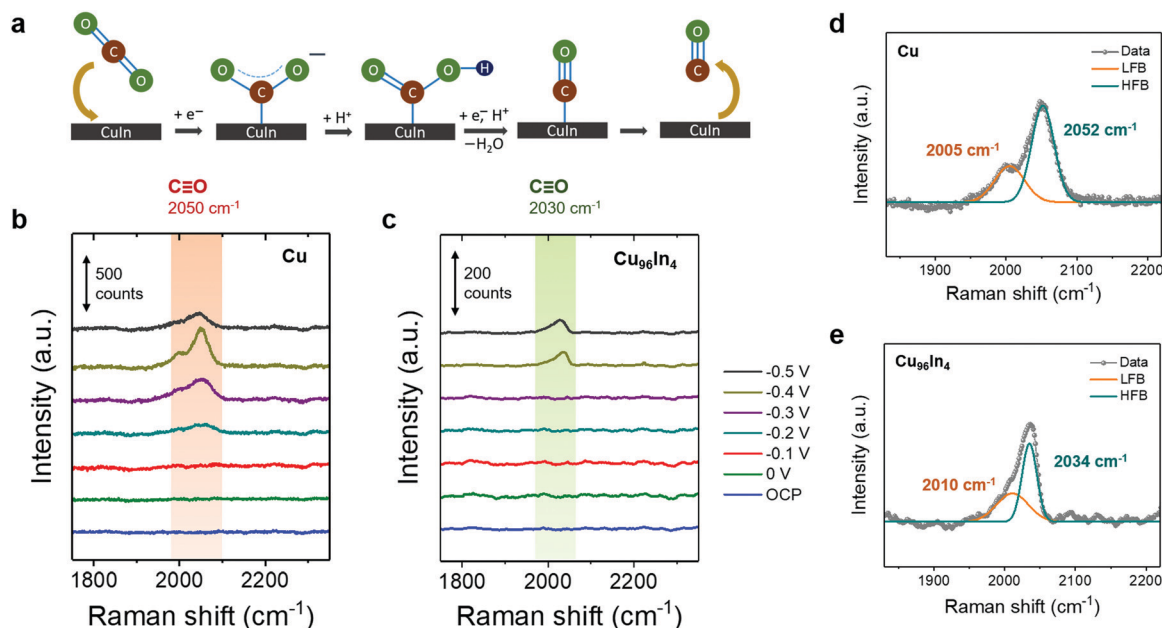


Fig. 3 (a) Schematic representation of proposed CO forming mechanism on CuIn surface. Operando Raman spectroscopy studies on (b) porous Cu foam and (c) porous Cu₉₆In₄ foam surfaces in CO₂ saturated 0.5 M KHCO₃ (pH 7.2) at room temperature using a 633 nm laser. The applied potentials shown here are with respect to the RHE scale. The $\nu(CO)$ peak at -0.4 V vs. RHE was deconvoluted into a lower frequency band (LFB) and a higher frequency band (HFB) for both pristine Cu (d) and Cu₉₆In₄ alloy surface (e).

site-bound $\nu(CO)$, which is the major key component of CO adsorption on a 3D hierarchical surface.^{34–36} In contrast, an asymmetric band around 2030 cm^{-1} emerges when the potential is stepped to -0.4 V vs. RHE for the Cu₉₆In₄ sample (Fig. 3c). This band may be deconvoluted into two peaks at 2010 cm^{-1} and 2034 cm^{-1} (Fig. 3e).

While this experiment does not allow for direct comparison of Raman intensities between the two different samples due to fundamental differences in site density and intrinsic interaction with the laser, we can compare the $\nu(CO)$ mode frequencies. It has been previously reported that, as the atop site bound CO on terraces results in a lower $\nu(CO)$ than a defect site bound CO, a stronger CO adsorption on Cu defect sites leads to a counter-intuitive blue-shift of $\nu(CO)$.^{34,36–38} A blue-shift of $\nu(CO)$ with increasing Cu–CO interaction has also been predicted by theory.³⁹ We observe that the pure Cu defect-site $\nu(CO)$ at 2052 cm^{-1} is red-shifted to 2034 cm^{-1} in the Cu₉₆In₄ sample, suggesting a weaker CO adsorption on the alloy surface.

Despite significant CO formation at -0.3 V vs. RHE, $\nu(CO)$ is not observed until -0.4 V vs. RHE on the Cu₉₆In₄ sample, and persists at -0.5 V vs. RHE. This indicates that a large local CO concentration is required for the surface-bound species to accumulate, further supporting a weaker CO adsorption on this surface compared to pure Cu. Although Raman spectroscopy is used and particularly useful in this study to observe the nature of CO adsorption to the whole catalyst surface, it cannot be employed to provide unequivocal support for a particular catalytic site.⁴⁰ Nevertheless, our electrochemical studies support an alloy as catalytic site.

Cu is a unique material that can form multicarbon products from CO₂ because it stabilizes the surface bound *CO sufficiently

to allow time for dimerization.⁴¹ This contrasts with Cu₉₆In₄ as we observe excellent CO selectivity over the entire range of applied potentials (-0.3 to -0.6 V vs. RHE, Fig. 2b) without any multicarbon product formation. We conclude that Cu₉₆In₄ can be highly selective towards CO due to beneficially weaker CO adsorption on the surface. The Cu₉₆In₄ bimetallic alloy with a dendritic foam morphology shows electroreduction of CO₂ with 70% FE_{CO} even at -0.3 V vs. RHE, which is a key advance over previously reported Cu–In materials.^{25,32,42}

PEC with perovskite|Cu_xIn_y cathodes

The Cu_xIn_y catalysts were next interfaced with cesium formamidinium methylammonium (CsFAMA) triple cation mixed halide perovskite inverse structure devices in an integrated configuration, which can be named a buried PV-biased cathode according to Nielander *et al.*⁴³ The perovskite architecture was modified with a doped poly[bis(4-phenyl)(2,4,6-trimethylphenyl)amine] (PTAA) hole transport layer, which improved the open-circuit voltage (V_{oc}) compared to previously reported devices (see the experimental procedure, photovoltaic histograms and J - V examples in Fig. S7 and S8, ESI†).¹⁸ The PV-biased cathodes were encapsulated using a conductive graphite epoxy paste, which provides increased stability in aqueous media and enables a direct catalyst adhesion to the underlying perovskite without additional binders.⁴⁴

Fig. 4a shows cyclic voltammetry (CV) scans of a buried perovskite|Cu₉₆In₄ cathode in CO₂ saturated 0.5 M aqueous KHCO₃ electrolyte solution. The photocurrent density reached -15 mA cm^{-2} at 0 V vs. RHE during irradiation (AM1.5G, 100 mW cm^{-2}), without any notable dark current. A potential of +0.55 V vs. RHE was selected for further CPE studies, as this



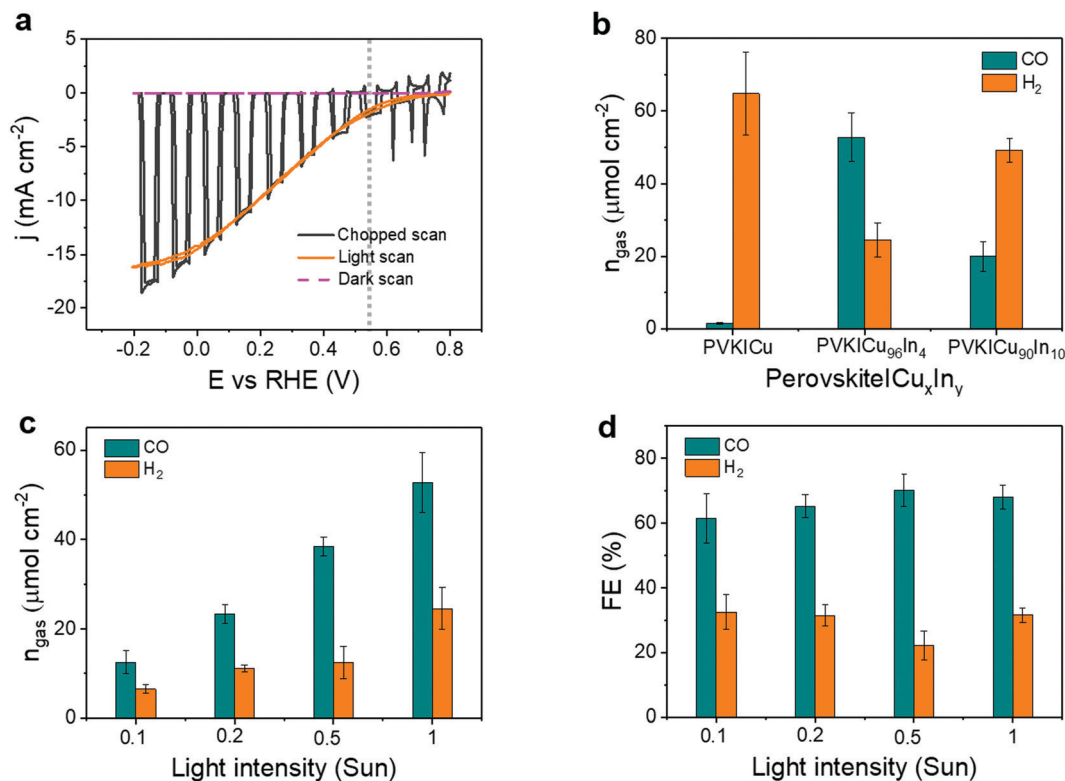


Fig. 4 Photoelectrochemistry with perovskite|Cu_xIn_y cathodes: (a) CV scan with perovskite|Cu₉₆In₄ cathode under chopped, continuous and no artificial sunlight illumination (1 sun, AM1.5G, 100 mW cm⁻², scan rate: 10 mV s⁻¹). (b) Activity of buried PV-biased cathodes containing catalysts with different composition under chopped 1 sun illumination (50 min on, 10 min off). (c) Amounts of products formed, and (d) their faradaic efficiencies on perovskite|Cu₉₆In₄ cathodes under different light intensities (chopped; 50 min on, 10 min off). All experiments were performed at room temperature and CO₂ saturated aqueous 0.5 M KHCO₃ (pH 7.2) was used as reaction medium. The applied bias in (b), (c) and (d) was +0.55 V vs. RHE and duration of all the PEC experiments was 4 h.

is the potential at which the photocurrents of the buried perovskite-biased cathode and BiVO₄ photoanode overlap in the tandem assembly (Fig. S9, ESI†), and this potential is therefore comparable with the bias-free conditions of the tandem device (see below).

To study the effect of the catalyst composition on the PEC response, we have performed CPE using different perovskite|Cu_xIn_y cathodes with varying In percentage in the catalyst. Fig. 4b shows the amounts of CO and H₂ from different buried PV-biased cathodes under 1 sun illumination. The corresponding FEs are shown in Fig. S10, ESI† (see also Tables S5 and S6, ESI†). A perovskite|Cu_xIn_y cathode containing a pure Cu catalyst (Cu foam, Cu₁₀₀In₀) shows selective H₂ production with only minor CO formation, whereas perovskite|Cu_xIn_y cathodes with a Cu₉₆In₄ catalyst displayed a good CO selectivity over H₂ with a CO:H₂ ratio of 2.2. However, when a catalyst with higher In percentage (Cu₉₀In₁₀) was employed on the buried perovskite|Cu_xIn_y cathode, the CO:H₂ ratio dropped to 0.4, showing a similar trend to the electrolysis data above (Fig. 2c). From PEC analysis we conclude that Cu₉₆In₄ is the optimum catalyst composition for a high CO selectivity of the buried perovskite|Cu_xIn_y cathodes, thus Cu₉₆In₄ was used in the tandem devices for bias-free CO production.

Next, the influence of light intensity on the performance of perovskite|Cu₉₆In₄ cathodes was studied. CPE and CV scans

showed that the photocurrent density increased almost linearly with the light intensity (Fig. S11–S13, ESI†). Hence, the amount of gaseous products also increased with the light intensity (Fig. 4c). No major changes in FE_{CO} were observed for light intensities between 1 sun and 0.1 sun (Fig. 4d). This behavior is consistent with the small change in selectivity observed with different applied potentials at the electrodes (Fig. 2b), as the light intensity affects the perovskite photovoltage, and hence the applied potential at the catalyst interface.²¹ The best CO:H₂ ratio of 3.2 ± 0.6 was obtained under 0.5 sun, corresponding to a (70.1 ± 5.0)% FE_{CO}, where the amount of CO was 38.45 ± 2.12 μmol cm⁻² (Tables S7 and S8, ESI†). The results demonstrate a robust PEC activity of the perovskite|Cu₉₆In₄ cathodes toward CO₂ conversion under different light irradiation, which makes them suitable for operation under low, diffuse sunlight.

BiVO₄||perovskite|Cu₉₆In₄ tandem device

To achieve bias-free solar CO₂-to-CO conversion using water as an electron donor, a tandem device was assembled in a compact, back-to-back ‘artificial leaf’ configuration by incorporating a BiVO₄ photoanode (containing an immobilized TiCo water oxidation catalyst) onto the integrated perovskite|Cu₉₆In₄ cathode.^{18,21} This configuration can be described as a buried PV-biased PEC cell as proposed by Nielander *et al.*,⁴³ standing out from wired perovskite



PV-electrode assemblies as both perovskite and BiVO_4 photoelectrodes are immersed under water during operation, which simplifies the overall device design. Thus, this integrated tandem system is technically different from a classical PV + electrolyser system, where catalysts are immersed in the electrolyte solution as anode and cathode and the required energies are supplied externally by a solar cell to perform CO_2 electrolysis.⁴⁵

Optical images of a tandem device are shown in Fig. S14 (ESI†). CV of the individual buried perovskite-biased cathode and BiVO_4 photoanode shows an overlap at +0.55 V vs. RHE with a photocurrent density of $208 \mu\text{A cm}^{-2}$, while the photoanode exhibits an early onset potential at 0.3 V vs. RHE (Fig. S9, ESI†). Since the perovskite solar cells achieve a V_{oc} of 1.07 ± 0.02 V (Fig. S7, ESI†), the tandem system would apply an effective potential around -0.5 V vs. RHE onto the $\text{Cu}_{96}\text{In}_4$ alloy catalyst, which is in the optimal potential range (-0.4 V to -0.6 V vs. RHE) for selective CO production (Fig. 2b). CV of the tandem device reveals an early onset bias of -0.4 V and a photocurrent density of around $212 \mu\text{A cm}^{-2}$ under no applied bias (Fig. 5a), which matches with the current density expected from the cathodic and anodic photocurrent overlap.

A stable photocurrent was maintained over 10 h experiment under no applied bias ($U_{\text{app}} = 0$ V, Fig. 5b), reaching an average steady-state photocurrent density of $195 \pm 20 \mu\text{A cm}^{-2}$. A higher initial photocurrent accounts for the reduction of a surface

oxide layer, which forms on the $\text{Cu}_{96}\text{In}_4$ catalyst under air (Fig. S3 and S6, ESI†).

The amounts of gaseous products increased gradually during the course of the experiment, accumulating to $21.17 \pm 0.04 \mu\text{mol cm}^{-2}$ CO, $7.21 \pm 1.34 \mu\text{mol cm}^{-2}$ H_2 and $14.71 \pm 3.15 \mu\text{mol cm}^{-2}$ O_2 after 10 h operation under zero applied bias (Fig. 5c and Table S9, ESI†). After the experiment, the electrolyte solution was analyzed by ^1H NMR spectroscopy and ion exchange chromatography (IC) for the presence of any liquid products. Only a negligible trace of formate (0.9 ± 0.2 ppm) was detected by IC (see Fig. S15, ESI† for representative chromatograms). A FE_{CO} of $(72.5 \pm 1.1)\%$ and FE_{H_2} of $(24.4 \pm 2.7)\%$ was obtained at the perovskite| $\text{Cu}_{96}\text{In}_4$ cathode and a faradaic efficiency for O_2 (FE_{O_2}) of $(72.1 \pm 14.3)\%$ at the BiVO_4 photoanode (Fig. 5d). FE_{CO} was roughly constant during the course of the experiment, whereas FE_{H_2} showed a slight increase over time (Table S10, ESI†). The tandems showed an excellent CO : H_2 ratio of 3 : 1 after 10 h, which is an order of magnitude increase of the CO selectivity compared to a molecular catalyst-based tandem under bias-free conditions.²¹ Due to the improved perovskite device architecture and lower catalyst overpotential, the tandem device also showed a noteworthy increase in the solar-to-fuel conversion, reaching 0.19% solar-to-CO (ten times higher) and 0.06% solar-to- H_2 efficiencies.^{13,46}

Some minor chemical and morphological transformations of the $\text{Cu}_{96}\text{In}_4$ catalyst were also observed during the 10 h

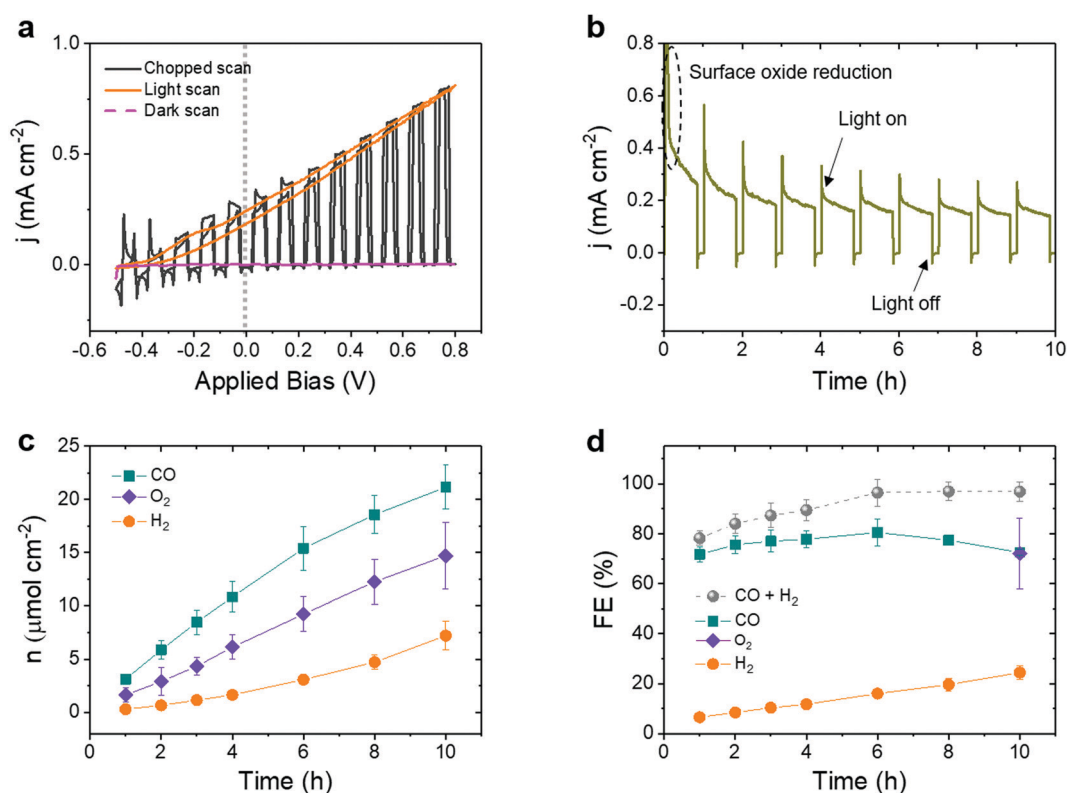


Fig. 5 Bias-free solar CO_2 conversion on a tandem BiVO_4 ||perovskite| $\text{Cu}_{96}\text{In}_4$ assembly. (a) CV scan under chopped, continuous and no artificial sunlight illumination (1 sun, AM1.5G, 100 mW cm^{-2} , scan rate: 10 mV s^{-1}). (b) representative photocurrent for 10 h bias-free operation under chopped 1 sun irradiation (50 min on, 10 min off), (c) amounts of products formed and (d) faradaic efficiency over the 10 h experiment. Bias-free ($U_{\text{app}} = 0$ V) experiments were carried out at room temperature in a one compartment cell using CO_2 saturated 0.5 M KHCO_3 electrolyte (pH 7.2).



bias-free PEC experiment. The as-prepared catalyst is a uniform alloy, where Cu and In are well distributed on the dendrite surface. During the experiment, the catalyst undergoes an *in situ* phase transformation, where the Cu and In phases partially separate from each other. XRD analysis reveals that some of the alloy phases even disappeared after the experiment (Fig. S16, ESI†). Post-experimental STEM mapping and XPS analysis confirmed that the In phase migrates towards the periphery as well as into the bulk of the dendrites (Fig. S17 and S3, ESI†). This phenomenon leads to an exposure of Cu phase on the catalyst surface, which may explain the slight increase of FE_{H_2} over time as pristine Cu phase is more active for H_2 evolution under these conditions (see Fig. 2c and 4b). However, the catalyst's bulk composition was unchanged as post-experiment ICP-OES analysis showed similar ratio of Cu and In ($\sim 96:4$) as the freshly prepared material. The overall porous dendritic morphology of the catalyst was intact after the experiment, but some structural agglomeration was observed in the nano-branches due to constant gas evolution (Fig. S18, ESI†).

Conclusions

A porous dendritic $\text{Cu}_{96}\text{In}_4$ foam is reported and shown to be electrocatalytically active towards CO production from aqueous CO_2 at low overpotentials. The weak adsorption of CO on the bimetallic alloy surface makes it a selective CO forming material, as supported by operando Raman spectroscopy. The excellent performance of the Cu-alloy electrocatalyst can be exploited in a perovskite|| BiVO_4 device for bias-free CO_2 reduction to produce CO with high selectivity using sunlight as energy input and water as the electron donor. A relatively high photocurrent density and early onset bias was obtained for the tandem device due to the lower CO_2 reduction overpotential of the catalyst and an improved perovskite device architecture providing a higher photovoltage. A CO selectivity of $\sim 75\%$ and solar-to-CO conversion efficiency of 0.19% were obtained after 10 h of photoelectrocatalysis under zero applied bias, which are an order of magnitude higher compared to a previous report.²¹ This study demonstrates that transition metal catalysts in combination with PEC systems allow for bias-free solar fuel production from CO_2 using sunlight as the sole energy source. The proof-of-concept can be further extended by interfacing different Cu-based catalysts onto the tandem to form various mono and multicarbon products under bias-free conditions.^{47–51}

Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

This work was supported by a SNSF EPM Fellowship Grant (P2BEP2_184483 code to M. R.), the OMV group (to C. P., V. A., E. R.), the Cambridge Trust (Cambridge Thai Foundation Award to C. P. and Vice-Chancellor's Award to V. A.), a Trinity-Henry Barlow Scholarship (to C. P.) as well as the Winton Programme

(to V. A.) and the EPSRC (EP/L027151, EP/S003053, EP/S025308, NanoDTC, EP/L015978/1 and EP/S022953 to D. W., J. B., E. R.). We acknowledge Prof. Dominic S. Wright (University of Cambridge) for providing the water oxidation catalyst precursor (TiCo). We also thank Dr Qian Wang and Dr Tengfei Li (University of Cambridge) for helpful feedback on the manuscript.

References

- 1 P. K. Nayak, S. Mahesh, H. J. Snaith and D. Cahen, *Nat. Rev. Mater.*, 2019, **4**, 269–285.
- 2 J. Warnan, J. Willkomm, Y. Farré, Y. Pellegrin, M. Boujtita, F. Odobel and E. Reisner, *Chem. Sci.*, 2019, **10**, 2758–2766.
- 3 A. Listorti, J. Durrant and J. Barber, *Nat. Mater.*, 2009, **8**, 929–930.
- 4 D. Kim, K. K. Sakimoto, D. Hong and P. Yang, *Angew. Chem., Int. Ed.*, 2015, **54**, 3259–3266.
- 5 J. J. Concepcion, R. L. House, J. M. Papanikolas and T. J. Meyer, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 15560–15564.
- 6 A. Y. Khodakov, W. Chu and P. Fongarland, *Chem. Rev.*, 2007, **107**, 1692–1744.
- 7 M. E. Dry, *Appl. Catal., A*, 1996, **138**, 319–344.
- 8 H. Zhang, Z. Yang, W. Yu, H. Wang, W. Ma, X. Zong and C. Li, *Adv. Energy Mater.*, 2018, **8**, 1800795.
- 9 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050–6051.
- 10 M. Crespo-Quesada, L. M. Pazos-Outón, J. Warnan, M. F. Kuehnel, R. H. Friend and E. Reisner, *Nat. Commun.*, 2016, **7**, 12555.
- 11 J. Luo, J.-H. Im, M. T. Mayer, M. Schreier, M. K. Nazeeruddin, N.-G. Park, S. D. Tilley, H. J. Fan and M. Grätzel, *Science*, 2014, **345**, 1593–1596.
- 12 Y.-F. Xu, M.-Z. Yang, B.-X. Chen, X.-D. Wang, H.-Y. Chen, D.-B. Kuang and C.-Y. Su, *J. Am. Chem. Soc.*, 2017, **139**, 5660–5663.
- 13 M. Schreier, L. Curvat, F. Giordano, L. Steier, A. Abate, S. M. Zakeeruddin, J. Luo, M. T. Mayer and M. Grätzel, *Nat. Commun.*, 2015, **6**, 7326.
- 14 J. Chen, J. Yin, X. Zheng, H. Ait Ahsaine, Y. Zhou, C. Dong, O. F. Mohammed, K. Takanabe and O. M. Bakr, *ACS Energy Lett.*, 2019, **4**, 1279–1286.
- 15 Q. Wang, L. Tao, X. Jiang, M. Wang and Y. Shen, *Appl. Surf. Sci.*, 2019, **465**, 607–613.
- 16 Y.-S. Chen, J. S. Manser and P. V. Kamat, *J. Am. Chem. Soc.*, 2015, **137**, 974–981.
- 17 Y. J. Jang, I. Jeong, J. Lee, J. Lee, M. J. Ko and J. S. Lee, *ACS Nano*, 2016, **10**, 6980–6987.
- 18 V. Andrei, R. L. Z. Hoyer, M. Crespo-Quesada, M. Bajada, S. Ahmad, M. De Volder, R. Friend and E. Reisner, *Adv. Energy Mater.*, 2018, **8**, 1801403.
- 19 S. Zhang, L. Shen, T. Ye, K. Kong, H. Ye, H. Ding, Y. Hu and J. Hua, *Energy Fuels*, 2020, **34**, 5016–5023.
- 20 E. Edwardes Moore, V. Andrei, S. Zacarias, I. A. C. Pereira and E. Reisner, *ACS Energy Lett.*, 2020, **5**, 232–237.
- 21 V. Andrei, B. Reuillard and E. Reisner, *Nat. Mater.*, 2020, **19**, 189–194.



- 22 D. Kim, J. Resasco, Y. Yu, A. M. Asiri and P. Yang, *Nat. Commun.*, 2014, **5**, 4948.
- 23 Y. Wang, D. Wang, C. J. Dares, S. L. Marquard, M. V. Sheridan and T. J. Meyer, *Proc. Natl. Acad. Sci. U. S. A.*, 2018, **115**, 278–283.
- 24 X. Zheng, Y. Ji, J. Tang, J. Wang, B. Liu, H.-G. Steinrück, K. Lim, Y. Li, M. F. Toney, K. Chan and Y. Cui, *Nat. Catal.*, 2019, **2**, 55–61.
- 25 S. Rasul, D. H. Anjum, A. Jedidi, Y. Minenkov, L. Cavallo and K. Takanabe, *Angew. Chem., Int. Ed.*, 2015, **54**, 2146–2150.
- 26 H.-C. Shin and M. Liu, *Chem. Mater.*, 2004, **16**, 5460–5464.
- 27 A. Dutta, M. Rahaman, N. C. Luedi, M. Mohos and P. Broekmann, *ACS Catal.*, 2016, **6**, 3804–3814.
- 28 Y. Hori, H. Wakebe, T. Tsukamoto and O. Koga, *Electrochim. Acta*, 1994, **39**, 1833–1839.
- 29 W. Zhu, R. Michalsky, Ö. Metin, H. Lv, S. Guo, C. J. Wright, X. Sun, A. A. Peterson and S. Sun, *J. Am. Chem. Soc.*, 2013, **135**, 16833–16836.
- 30 H. A. Hansen, J. B. Varley, A. A. Peterson and J. K. Nørskov, *J. Phys. Chem. Lett.*, 2013, **4**, 388–392.
- 31 X. Nie, M. R. Esopi, M. J. Janik and A. Asthagiri, *Angew. Chem., Int. Ed.*, 2013, **52**, 2459–2462.
- 32 W. Luo, W. Xie, R. Mutschler, E. Oveisi, G. L. De Gregorio, R. Buonsanti and A. Züttel, *ACS Catal.*, 2018, **8**, 6571–6581.
- 33 Y. Hori, O. Koga, Y. Watanabe and T. Matsuo, *Electrochim. Acta*, 1998, **44**, 1389–1395.
- 34 C. M. Gunathunge, X. Li, J. Li, R. P. Hicks, V. J. Ovalle and M. M. Waagele, *J. Phys. Chem. C*, 2017, **121**, 12337–12344.
- 35 Z. Pan, K. Wang, K. Ye, Y. Wang, H.-Y. Su, B. Hu, J. Xiao, T. Yu, Y. Wang and S. Song, *ACS Catal.*, 2020, **10**, 3871–3880.
- 36 W. Akemann and A. Otto, *J. Raman Spectrosc.*, 1991, **22**, 797–803.
- 37 B. Eren, Z. Liu, D. Stacchiola, G. A. Somorjai and M. Salmeron, *J. Phys. Chem. C*, 2016, **120**, 8227–8231.
- 38 S. Vollmer, G. Witte and C. Wöll, *Catal. Lett.*, 2001, **77**, 97–101.
- 39 P. S. Bagus and G. Pacchioni, *Electrochim. Acta*, 1991, **36**, 1669–1675.
- 40 A. Wuttig, M. Yaguchi, K. Motobayashi, M. Osawa and Y. Surendranath, *Proc. Natl. Acad. Sci. U. S. A.*, 2016, **113**, E4585–E4593.
- 41 A. A. Peterson, F. Abild-Pedersen, F. Studt, J. Rossmeisl and J. K. Nørskov, *Energy Environ. Sci.*, 2010, **3**, 1311–1315.
- 42 G. O. Larrazábal, A. J. Martín, S. Mitchell, R. Hauert and J. Pérez-Ramírez, *ACS Catal.*, 2016, **6**, 6265–6274.
- 43 A. C. Nielander, M. R. Shaner, K. M. Papadantonakis, S. A. Francis and N. S. Lewis, *Energy Environ. Sci.*, 2015, **8**, 16–25.
- 44 V. Andrei, K. Bethke and K. Rademann, *Phys. Chem. Chem. Phys.*, 2016, **18**, 10700–10707.
- 45 M. Schreier, F. Héroguel, L. Steier, S. Ahmad, J. S. Luterbacher, M. T. Mayer, J. Luo and M. Grätzel, *Nat. Energy*, 2017, **2**, 17087.
- 46 H. Dotan, N. Mathews, T. Hisatomi, M. Grätzel and A. Rothschild, *J. Phys. Chem. Lett.*, 2014, **5**, 3330–3334.
- 47 M. Rahaman, A. Dutta, A. Zanetti and P. Broekmann, *ACS Catal.*, 2017, **7**, 7946–7956.
- 48 E. L. Clark, C. Hahn, T. F. Jaramillo and A. T. Bell, *J. Am. Chem. Soc.*, 2017, **139**, 15848–15857.
- 49 C. G. Morales-Guio, E. R. Cave, S. A. Nitopi, J. T. Feaster, L. Wang, K. P. Kuhl, A. Jackson, N. C. Johnson, D. N. Abram, T. Hatsukade, C. Hahn and T. F. Jaramillo, *Nat. Catal.*, 2018, **1**, 764–771.
- 50 F. Li, Y. C. Li, Z. Wang, J. Li, D.-H. Nam, Y. Lum, M. Luo, X. Wang, A. Ozden, S.-F. Hung, B. Chen, Y. Wang, J. Wicks, Y. Xu, Y. Li, C. M. Gabardo, C.-T. Dinh, Y. Wang, T.-T. Zhuang, D. Sinton and E. H. Sargent, *Nat. Catal.*, 2020, **3**, 75–82.
- 51 D. Wakerley, S. Lamaison, F. Ozanam, N. Menguy, D. Mercier, P. Marcus, M. Fontecave and V. Mougél, *Nat. Mater.*, 2019, **18**, 1222–1227.

